

The Role of Na₂CO₃ as Precipitating Agent in Salt Purification Process

Dwi Hery Astuti*, Trista Purba, Nizar Su'udi, Sani, Reva Edra Nugraha

Department of Chemical Engineering, Universitas Pembangunan Nasional "Veteran" Jawa Timur, Surabaya, Indonesia

*Corresponding author:

E-mail: dwiher59@gmail.com

ABSTRACT

Salt is an essential compound in life. It is used for food preservation. It is also used for health or isotonic drink, additive in soap production, dialysate, and use an infusion liquid. In the industrial sector, the minimum purity of NaCl in salt was 98.5%. Therefore, the impurities in raw salt from coarse salt should be removed to increase the purity of NaCl and increase the economic value of raw salt. The extraction and recrystallization method can separate the impurities in raw salt by adding the precipitating agent Na₂CO₃. The mol ratio of Na₂CO₃ and the stirring time were varied to optimize the weight of Ca extracted and give the high purity. The result showed that using Na₂CO₃ mol ratio of 1-2.5 will drastically reduce the Ca content (0.03-0.01%) in stirring time 60-150 min. The maximum purity of NaCl obtained from the extraction and recrystallization process was 98.66% using a ratio mol of 1:1 and stirring time of 150 min.

Keywords: Recrystallization, raw salt, NaCl, Na₂CO₃

Introduction

Salt is one mineral mainly composed of NaCl. Salt is an essential nutrient compound in human life as an electrolyte and osmotic solute. Salt is used as food preservation, food flavoring, health/isotonic drink, as an additive in soap production, dialysate fluid, and an infusion fluid. In general, salt is produced from salt mines by seawater evaporation in the salt fields. The seawater evaporation may cause a high concentration of seawater, and at a specific level of salt concentration, the crystallization of salt happens gradually (Ihsan et al., 2002).

In the industrial process, salt is the primary commodity as the raw materials in chlorine (Cl₂) production and caustic solution (sodium hydroxide (NaOH) and Potassium hydroxide (KOH)), which is produced by the electrolysis process of salt solutions decomposition. Nowadays, 95% of chlorine production in the world uses the electrolysis method. The salt impurities such as Ca²⁺ and Mg²⁺ can cause disturbance ion Na⁺ crossing on cell membranes. Based on Indonesian National Standard (SNI), the minimum purity of NaCl for salt industries was 98.5%, and the maximum content of Ca²⁺ and Mg²⁺ cation were 0.1% and 0.06%, respectively (Gemati et al., 2013).

The improvement of NaCl purity in crude salt can be made by the recrystallization method. The recrystallization method purifies the raw materials by the precipitation of solid impurities and further heated and evaporation processes to produce high purity crystals (Rusiyanto et al., 2013). The impurities in coarse salt can be removed by NaOH addition to transforming MgCl₂ and MgBr₂ to precipitated Mg(OH)₂. The addition of Na₂CO₃ will remove CaCl₂ in forming precipitated CaCO₃ (Rahman et al., 2010). The cation of Ca²⁺ can be removed by graded crystallization with the first fraction was CaCO₃ and CaSO₄ as the precipitated salt (Mishra et al., 2010). In this research, the Ca²⁺ cation as the impurities in coarse salt was removed by recrystallization using Na₂CO₃ as the precipitating agent. The effect of the Na₂CO₃ mol ratio and the stirring time was investigated in this study.

How to cite:

Astuti, D. H., Purba, T., Su'udi, N., Sani, & Nugraha, R. E. (2021). The role of Na₂CO₃ as precipitating agent in salt purification process. *2nd International Conference Eco-Innovation in Science, Engineering, and Technology*. NST Proceedings. pages 25-29. doi: 10.11594/nstp.2021.1405

Material and Methods

Materials

The coarse salt as raw salt materials used in this research was acquired from Blawi, Lamongan, East Java Province.

Methods

The mol ratio of CaSO_4 and Na_2CO_3 used in this study was detailed in Table 1. The extraction process was conducted by mixing 300g of coarse salt with 1000 mL of demineralized water. Na_2CO_3 (100 mL) was added gradually to the mixture and stirred with 150 rpm for 30, 60, 90, 120, and 150 min, followed by a precipitation process for 90 min. Then, the solution is filtered to separate CaCO_3 from the solution. The filtrate is evaporated and crystallized. The salt crystal was dried in an oven at 100-110 °C for 4 hours. The process was repeated by using different mol of Na_2CO_3 , as shown in Table 1. The products were further analyzed for the level impurities of Ca and NaCl purity.

Table 1. Mol ratio and the weight of CaSO_4 in coarse salt and Na_2CO_3

gmol/Ratio	CaSO_4	Na_2CO_3
1 : 0.5	10.74	4.18
1 : 1	10.74	8.36
1 : 1.5	10.74	12.54
1 : 2	10.74	16.72
1 : 2.5	10.74	20.90

Results and Discussion

The coarse salt still containing impurities such as Ca^{2+} , Mg^{2+} , Al^{3+} , Fe^{3+} , SO_4^{2-} , I⁻, Br⁻, CaSO_4 , and MgSO_4 . The coarse salt needs to be processed to reduce the impurities content and increase the purity of NaCl. The role of Na_2CO_3 as the precipitating agent of Ca^{2+} was investigated in this study. The effect of Na_2CO_3 mol and stirring time can be optimized to obtain the highest purity of NaCl.

Firstly, the physicochemical properties of coarse salt were investigated using titrimetry and gravimetry methods. The analysis results were tabulated in Table 2. Based on titrimetry analysis, coarse salt has low purity of NaCl (49.17%). The purity of NaCl in coarse salt is not eligible for consumption and industrial process. CaSO_4 and MgCl_2 as the impurities in coarse salt were detected in gravimetry analysis.

Table 2. The physicochemical properties of Coarse Salt

No	Testing parameter	Result	Method
1.	NaCl	49,17%	Titrimetry
2.	CaSO_4	3,58%	
3.	MgCl_2	2,12%	Gravimetry
4.	H_2O	7,60%	
5.	Insoluble	980 ppm	

The effect of Na_2CO_3 mol and stirring time was investigated in this study. The results were summarized in Table 3 as the amount of Ca extracted from Coarse Salt. The results showed that the mol of Na_2CO_3 and the stirring time influence the Ca that removed from Coarse Salt. To achieve the standard for industrial salt with the NaCl purity of 98.5%, the Ca content should be 0.1% in maximum. As shown in Table 3, with the increase of Na_2CO_3 mol ratio, the weight of Ca extracted will also increase. This result was similar to the rise of stirring time. The increasing stirring time will also increase the weight of Ca extracted from Coarse Salt. The impurities of Ca^{2+} were precipitated in the form of carbonate as follows the chemical reaction of Ca^{2+} cation with Na_2CO_3 (Gemati et al., 2013).



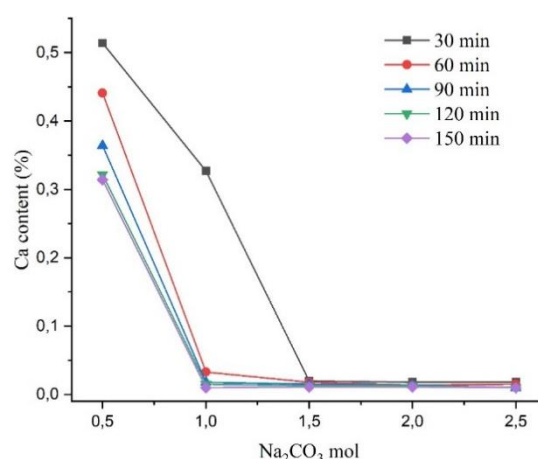


Table 3. The weight of Ca extracted (g) in the variation of mol ratio and stirring time

Stirring-time (min)	Mole Ratio				
	1 : 0,5	1 : 1	1 : 1,5	1 : 2	1 : 2,5
30	9.198	9.759	10.680	10.686	10.686
60	9.417	10.641	10.686	10.698	10.695
90	9.648	10.686	10.695	10.698	10.710
120	9.774	10.695	10.701	10.701	10.710
150	9.798	10.710	10.707	10.707	10.710

Figure 1. The effect of Na₂CO₃ mol in Ca content (%) of salt produced

The Ca content in salt produced after the recrystallization process is shown in Figure 1 and Figure 2. The correlation between the mol of Na₂CO₃ with the Ca content (%) in salt produced was clearly shown in Figure 1. Theoretically, if the mol of Na₂CO₃ is equivalent to Ca²⁺ mol in coarse salt, the salt produced will have 0% Ca. Based on the analysis, the addition of 1:1 Na₂CO₃ with the stirring time of 30 min, the Ca content was 0.327%. Furthermore, in the mol ratio of Na₂CO₃ 0.5, the Ca content still has a high value (0.3-0.5%) in 30-150 stirring time. The Ca content did not meet the requirement in SNI standard.

Interestingly, increasing the number of Na₂CO₃ up to 1.5 moles can significantly reduce the Ca content up to 0.02% by stirring time 30 minutes. It was worthy to note that using Na₂CO₃ mol ratio of 1-2.5 will drastically reduce the Ca content (0.03-0.01%) in stirring time 60-150 min. These results agreed with the previous study by Ihsan et al. (2002), which increases the precipitating agent Na₂CO₃ will the stirring time also plays an important role in coarse salt purification using the recrystallization process. The correlation between the stirring time with the Calcium content is shown in Figure 2. In mol ratio Na₂CO₃ of 1:0.5, the increasing of stirring time only gives a little impact in reducing Ca content from 0.5% in 30 min become 0.3% in 150 min. Meanwhile, in mol ratio Na₂CO₃ of 1:1, the increasing stirring time to 60 min gives a significant impact for Ca content reduction from 0.33% in 30 min become 0.01% in 60 min of stirring time. Furthermore,

in mol ratio Na_2CO_3 of 1:1.5, 1:2, and 1:2.5, the increasing stirring time has no impact on Ca content reduction since the Ca content was 0.01% in 30 min of stirring time.

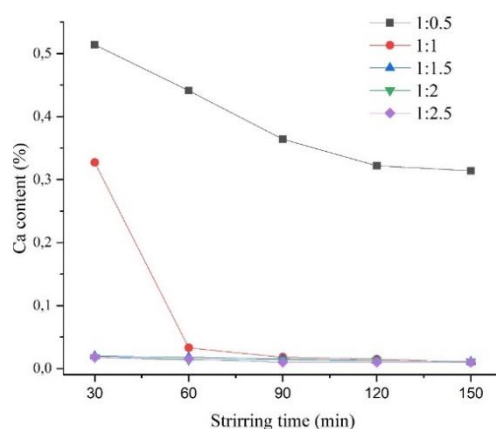


Figure 2. The effect of stirring time in Ca content (%) of salt produced

The salt produced by recrystallization proceeded using coarse salt was further analyzed for the NaCl content as shown in Table 4. The highest purity of NaCl was obtained in stirring time of 150 min with the Na_2CO_3 mol ratio of 1:1. The increasing stirring time will increase the NaCl purity in salt produced from coarse salt.

Table 4. The NaCl content in the variation of stirring time

Stirring time (min)	NaCl content (%)
30	88.490
60	91.900
90	92.690
120	94.680
150	98.660

Conclusion

The improvement of NaCl purity in coarse salt can be implemented by the extraction process using Na_2CO_3 . The role of Na_2CO_3 as the precipitating agent of Ca^{2+} was investigated in this study. The increasing mol of Na_2CO_3 in the extraction process will reduce the Ca content in CoarseSalt. Furthermore, the increasing stirring time will also increase the Ca extracted and reduce the Ca content. The maximum purity of NaCl obtained from the extraction process was 98.66% using ratio mol Na_2CO_3 of 1:1 and stirring time of 150 min.

Acknowledgment

The author would like to acknowledge Universitas Pembangunan Nasional "Veteran" Jawa Timur for supporting the experiment. The authors also thank Trista Purba and Nizar Su'udi for conducting the research experiment and data analysis

References

- Gemati, A., Gunawan & Khabibi. (2013). Pemurnian garam NaCl melalui Metode Rekrystalisasi Garam Krosok dengan Penambahan Na_2CO_3 , NaOH dan Polialuminium Klorida untuk Penghilangan Pengotor Ca^{2+} dan Mg^{2+} . *Jurnal Sains Kimia dan Aplikasi*, 16(2), 50-54. DOI: <https://doi.org/10.14710/jksa.16.2.50-54>
- Ihsan, D., Istadi & Djaeni, M. (2002). Improving public salt quality by chemical treatment. *Journal of Coastal Development*, 5(3), 111-116.

- Mishra, S., Ghosh, P. K., Gandhi, M. R., Bhatt, A. M., & Chauhan, S. A. (2010). Removal of Ca²⁺ impurities from brine by *Marine cyanobacteria* from gujarat coast of india for the production of industrial grade salt.
- Rahman, A., Islam, A., & Farrukh, M. A., (2010). An improved method for the preparation of analytical grade sodium chloride from khewra rock salt. *World Applied Science Journal*, 8(1), 61-65
- Rusiyanto., Soesilowati, E., & Jumaeri, (2013), Penguatan industri gara, nasional melalui perbaikan teknologi budidaya dan diversifikasi produk. *Saintekno*, 11(2), 129-142.